

THIS REPORT HAS BEEN DELIMITED  
AND CLEARED FOR PUBLIC RELEASE  
UNDER DOD DIRECTIVE 5200.20 AND  
NO RESTRICTIONS ARE IMPOSED UPON  
ITS USE AND DISCLOSURE.

DISTRIBUTION STATEMENT A

APPROVED FOR PUBLIC RELEASE;  
DISTRIBUTION UNLIMITED.

UNCLASSIFIED  
AD 432377

DEFENSE DOCUMENTATION CENTER  
FOR  
SCIENTIFIC AND TECHNICAL INFORMATION  
CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

**Reproduced From  
Best Available Copy**

432377

FILE COPY

432377

NO. OTS

731 500

October 9, 1963

CaF<sub>2</sub> Laser Crystal Growth

Order No. 306-62

Contractor: RCA Laboratories

Contract Date: 4-1-63

Project Code No. 3730

A. Weakliem, WA 4-2700 X 2447

Contract No. Nonr 4133(00)

Amount of Contract \$89,493

Expires 3-31-64

Status Report No. 2

Director, ARPA:

Considerable progress has been made in the crystal growth of CdF<sub>2</sub> by use of the Bridgeman technique. The pure crystals (no deliberate addition of impurities) presently being grown contain 1-10 ppm of several elements, usually Zn, Ag, Cu, Fe, and Pb. The apparent band edge lies close to 2500 Å which is some 500 Å longer wavelength than that reported for ultra-pure CdF<sub>2</sub>. We have grown crystals of CdF<sub>2</sub> containing Cr<sup>+3</sup>, Mn<sup>+2</sup>, Co<sup>+2</sup>, Ni<sup>+2</sup>, and Nd<sup>+3</sup>. The crystals are of good quality optically, are probably not one single crystal, but contain large single crystal regions, and are 1/2" x 1" cylindrical boules. The assignment of the oxidation state is based on preliminary analyses of the room temperature and 77°K absorption spectra.

In the case of chromium, the impurity was added both as CrF<sub>2</sub> and CrF<sub>3</sub>, otherwise identical crystal growth conditions, and the spectra of the resulting crystals were identical. There are two band systems, centered about 4450 Å and 6800 Å. The bands show a slight diminution in intensity on going from 300°K to 2°K and the bandwidth of about 4000 cm<sup>-1</sup> is almost temperature independent. The indications are that chromium occupies a Cd site as Cr<sup>+3</sup> and has the full O<sub>h</sub> symmetry of the site. In particular the bandwidth and temperature dependence of intensity indicates that the ion is at a centrosymmetric site. The value of Dq is in the range 1000 - 1500 cm<sup>-1</sup> and the ground state may be partially spin quenched due to a large amount of <sup>2</sup>E(eg<sup>3</sup>) character. We intend to study this aspect by the use of electron paramagnetic resonance.

The spectra of Mn<sup>+2</sup> and Ni<sup>+2</sup> are not yet understood. The spectra are not those expected on the basis of symmetry arguments and Dq values predicted from examination of the spectra of those ions having other geometrical environments with symmetries O<sub>h</sub> or T<sub>d</sub>. We expected these predictions to give rather precise agreement with observation as was the case with the Co<sup>+2</sup> ion, but this seems not to be so. The Mn<sup>+2</sup> spectra shows only a very gradually rising absorption beginning near 1 micron and having the appearance of an absorption edge at about 5000 Å. The spectra of Ni<sup>+2</sup> has two moderately intense bands at 4500 and 5300 Å. It is not yet clear if these bands are due to crystal field states of the impurity or if they are of the charge transfer type.

There has also been some success in the attempts to introduce transition element impurities into CaF<sub>2</sub>. Crystals were grown by pulling from melts containing 0.1% of MnF<sub>2</sub>, CrF<sub>3</sub>, and NiF<sub>2</sub>. The crystals are green and the absorption spectra are almost identical.


Emission spectra studies have not yet been undertaken. A 2 meter plane grating B and L spectrograph has been received and we are in the process of installing it. The instrument should be in use within a few weeks.

A Fabry-Perot interferometer has been assembled and aligned. The interference pattern of the 6328 Å gas laser has been photographed but the theoretical resolving power of  $0.005 \text{ cm}^{-1}$  has not yet been realized. In preliminary photographs of  $\text{CaF}_2:\text{Tm}^{+2}$  fluorescence at  $4^\circ \text{ K}$ , we observe an apparent line width of  $0.01 \text{ cm}^{-1}$  and a  $0.03 \text{ cm}^{-1}$  hyperfine splitting. We are also undertaking an experiment to observe the fluorescence through a second  $\text{CaF}_2:\text{Tm}^{+2}$  crystal which acts to absorb some of the incident fluorescence. We will then apply a longitudinal magnetic field and the Zeeman splitting produced acts to reduce the absorption at the center frequency. By varying the field one thus has a method of scanning across the fluorescence line with what amounts to a narrow band filter. We intend to use this method for the line width study.

*Herbert A. Weakliem*

Herbert A. Weakliem

HAW/ldb

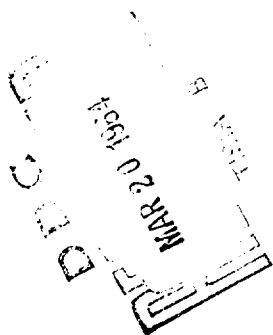

**Reproduced From  
Best Available Copy**